

NIMONIC® alloy 901 (UNS N09901/W.Nr. 2.4662) is an age-hardenable Ni-Fe-Cr superalloy with significant additions of molybdenum, titanium and aluminum. The alloying route for this high-performance material may include combinations of vacuum induction melting, vacuum arc remelting and electroslag remelting, according to the final application and the customer's specification. Typically, the alloy is used for gas turbine engine discs, shafts, rings, casings and seals with a maximum service temperature of around 600°C (1100°F).

Table 1 - Nominal Chemical Composition, %
(not for specification purposes)

Nickel.....	42.5
Chromium.....	12.5
Molybdenum.....	5.75
Titanium.....	2.9
Cobalt.....	1.0 max.
Copper.....	0.5 max.
Manganese.....	0.5 max.
Silicon.....	0.4 max.
Aluminum.....	0.35 max.
Carbon.....	0.1 max.
Sulfur.....	0.03 max.
Iron.....	Balance*

*Reference to the balance of the alloy composition does not guarantee this is exclusively of the element mentioned but that it predominates and others are present only in minimal quantities.

Heat Treatment

The heat treatment for NIMONIC alloy 901 forged bar is a three-stage process involving a solution treatment followed by two age-hardening stages. The recommended procedure is 3h/1090°C (1994°F)/WQ + 4h/775°C (1427°F)/AC + 24h/705-720°C (1301-1328°F)/AC.

Physical Properties

Some physical properties for NIMONIC alloy 901 are listed in Tables 2-4. Thermal expansion data in Table 3 were determined on fully heat-treated material. The data are subject to a variation of approximately ±5% according to processing variables. The dynamic modulus data in Table 4 were obtained from fully heat-treated cylindrical specimens vibrated in the flexural mode. The recommended heat treatment is quoted above.

Table 2 - Physical Properties

Density, Mg/m ³	8.14
lb/in ³	0.294
Melting Range, °C.....	1280-1345
°F.....	2336-2453
Specific Heat, J/kg•°C.....	431 at 20°C
Btu/lb•°F.....	0.103 at 68°F
Electrical Resistivity, μΩ•cm.....	112 at 20°C
ohm/circ•mil•ft.....	674 at 68°F

Table 3 - Mean coefficient of linear thermal expansion

°C	°F	μm/m•°C	10 ⁻⁶ in/in•°F
20-100	70-200	13.5	7.50
200	392	14.2	7.89
300	572	14.3	7.94
400	752	14.5	8.06
500	932	14.8	8.22
600	1112	15.0	8.33
700	1292	15.3	8.50
800	1472	16.1	8.94
900	1652	17.5	9.72
1000	1832	19.9	11.06

Table 4 - Dynamic Young's Modulus

Temperature		GPa	10 ³ ksi
°C	°F		
20	68	201	29.2
100	212	198	28.7
200	392	192	27.8
300	572	185	26.8
400	752	179	26.0
500	932	172	24.9
600	1112	166	24.1
700	1292	159	23.1
800	1472	150	21.8
900	1652	138	20.0
1000	1832	126	18.3

Publication Number SMC-076
Copyright © Special Metals Corporation, 2004 (Sept 04)

NIMONIC is a trademark of the Special Metals Corporation group of companies.



NIMONIC® alloy 901

Mechanical Properties

Tensile properties for forged bar over a range of temperatures are shown in Figure 1. Creep-rupture properties for forged bar are shown by Larson-Miller presentation in Figure 2. Impact properties, at room temperature and at high temperatures, are shown in Tables 5 and 6. For the impact data, the test pieces, taken in circumferential direction, were V-notched.

Available Products and Specifications

NIMONIC alloy 901 is designated as UNS N09901 and Werkstoff Number 2.4662. Alloy 901 is available as flat or round bar, extruded section and forging billet.

Rod, Bar, Wire and Forging Stock - BR HR 55, SAE AMS 5660, SAE AMS 5661, AECMA PrEN2176, AECMA PrEN2177, ISO 9723, ISO 9725

Others - AECMA PrEN2178

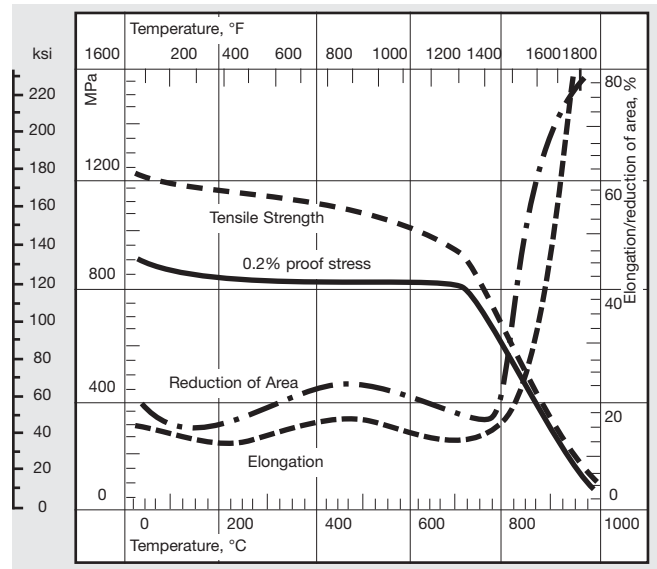


Figure 1. Tensile properties of vacuum refined, extruded and forged bar.

Table 5 - Room-Temperature Impact Properties of NIMONIC alloy 901, J (ft•lbf)

Soaking time, hours	Soaking Temperature				
	550°C (1022°F)	600°C (1112°F)	650°C (1202°F)	700°C (1292°F)	750°C (1382°F)
30	58 (42.8)	44 (32.5)	49 (36.2)	41 (30.3)	50 (36.6)
100	47 (34.7)	50 (36.6)	45 (33.2)	32 (23.6)	27 (19.9)
300	47 (34.7)	57 (42.1)	37 (27.3)	18 (13.3)	14 (10.3)
1000	41 (30.3)	38 (28.0)	14 (10.3)	12 (8.9)	5 (3.7)
3000	42 (31.0)	47 (34.7)	12 (8.9)	-	5 (3.7)
10,000	41 (30.3)	15 (11.1)	12 (8.9)	5 (3.7)	5 (3.7)

Table 6 - High-Temperature Impact Properties of NIMONIC alloy 901, J (ft•lbf)

Soaking time, hours	Soaking and Test Temperature				
	550°C (1022°F)	600°C (1112°F)	650°C (1202°F)	700°C (1292°F)	750°C (1382°F)
0	60 (44.3)	50 (36.9)	56 (41.3)	42 (31.0)	50 (36.6)
30	49 (36.2)	41 (30.3)	37 (27.3)	46 (34.0)	27 (27.3)
100	45 (33.2)	41 (30.3)	45 (33.2)	34 (25.1)	42 (31.0)
300	44 (32.5)	45 (33.2)	34 (25.1)	41 (30.3)	31 (22.9)
1000	73 (53.9)	49 (36.2)	26 (19.2)	28 (20.7)	24 (17.7)
3000	47 (34.7)	41 (30.3)	20 (14.8)	-	15 (11.1)
10,000	52 (38.4)	22 (16.2)	22 (16.2)	12 (8.9)	18 (13.3)

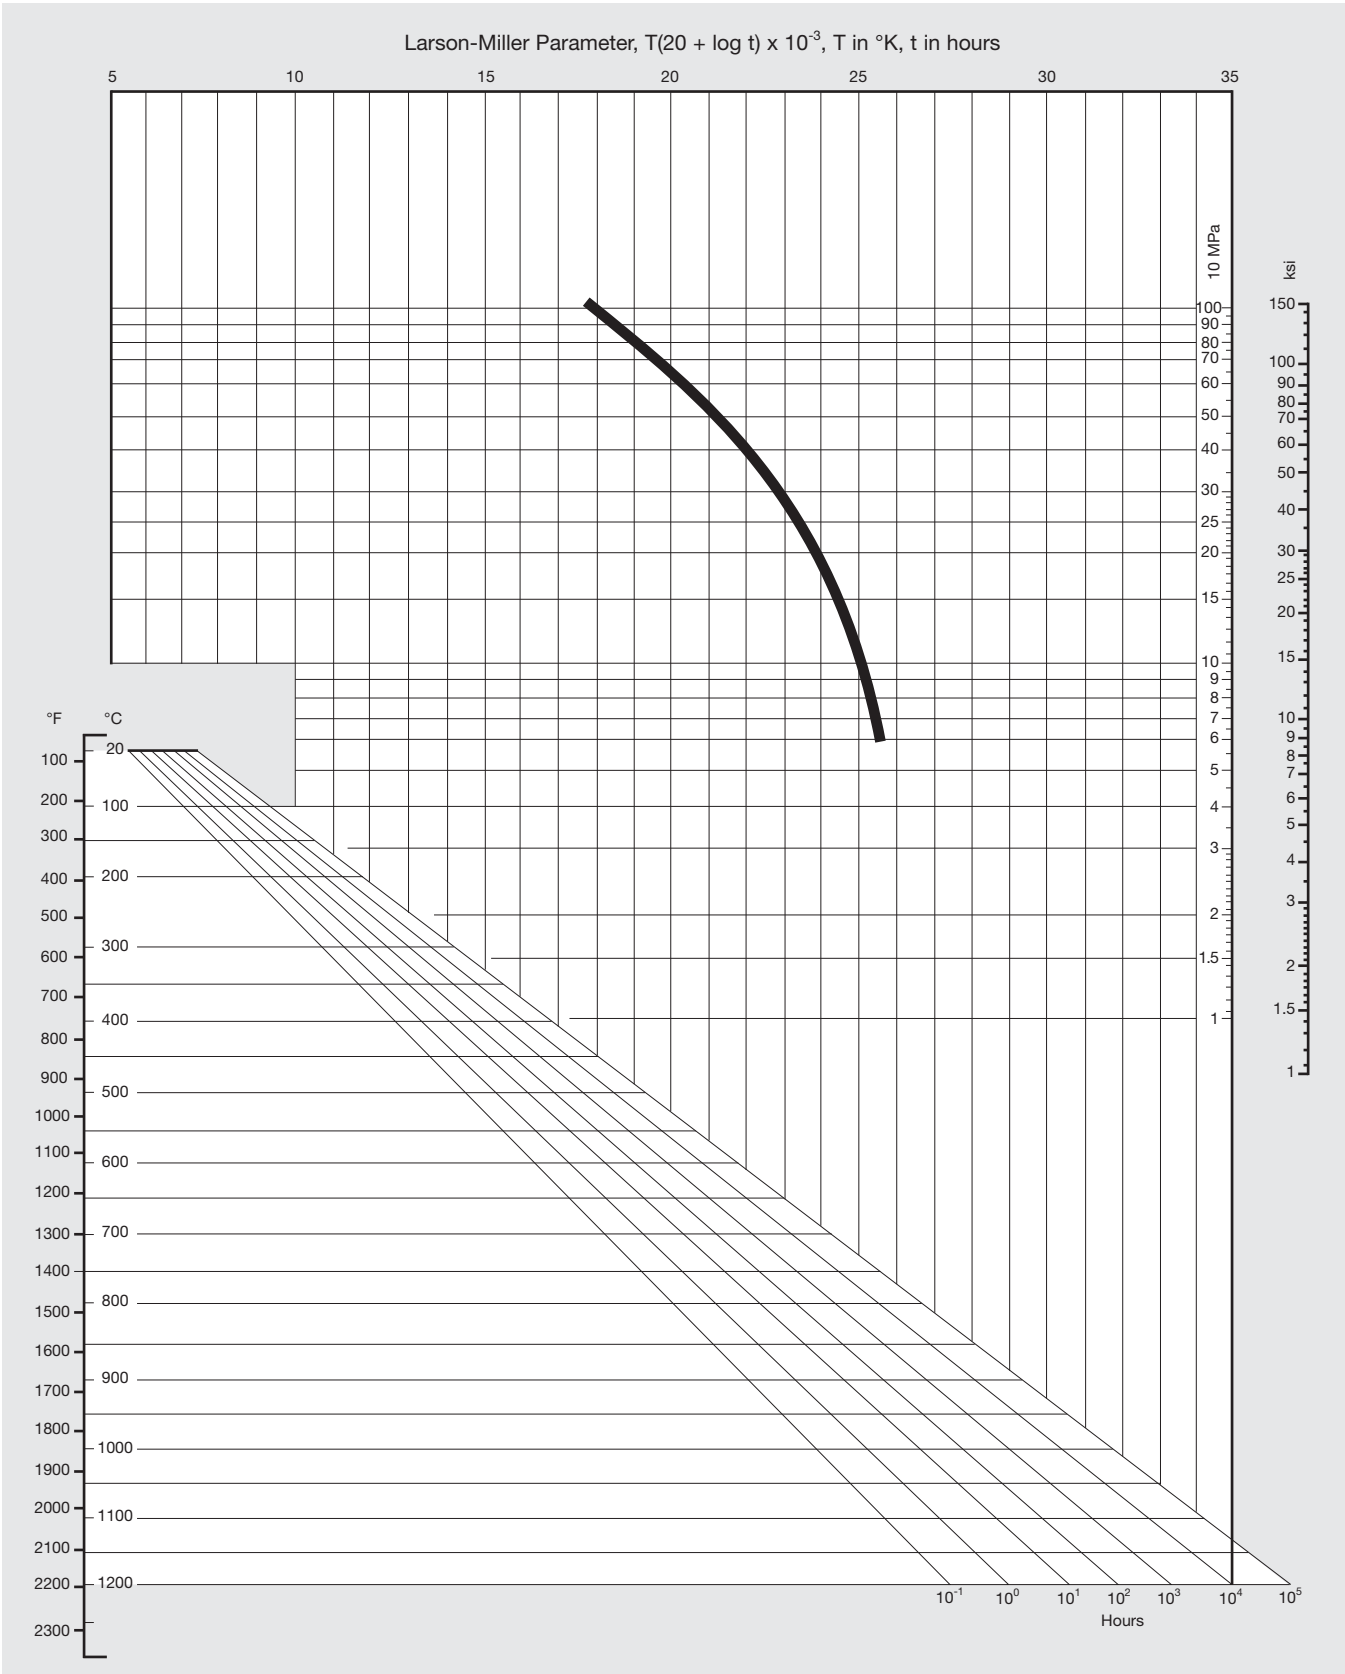


Figure 2. Creep-rupture properties of NIMONIC alloy 901 forged bars.

U.S.A. Special Metals Corporation

Billet, rod & bar, flat & tubular products

3200 Riverside Drive
Huntington, WV 25705-1771
Phone +1 (304) 526-5100
+1 (800) 334-4626
Fax +1 (304) 526-5643

Billet & bar products

4317 Middle Settlement Road
New Hartford, NY 13413-5392
Phone +1 (315) 798-2900
+1 (800) 334-8351
Fax +1 (315) 798-2016

Atomized powder products

100 Industry Lane
Princeton, KY 42445
Phone +1 (270) 365-9551
Fax +1 (270) 365-5910

Shape Memory Alloys

4317 Middle Settlement Road
New Hartford, NY 13413-5392
Phone +1 (315) 798-2939
Fax +1 (315) 798-6860

United Kingdom

Special Metals Wiggin Ltd.

Holmer Road
Hereford HR4 9SL
Phone +44 (0) 1432 382200
Fax +44 (0) 1432 264030

Special Metals Wire Products

Holmer Road
Hereford HR4 9SL
Phone +44 (0) 1432 382556
Fax +44 (0) 1432 352984

China

Special Metals Pacific Pte. Ltd.

Room 1802, Plaza 66
1266 West Nanjing Road
Shanghai 200040
Phone +86 21 3229 0011
Fax +86 21 6288 1811

Special Metals Pacific Pte. Ltd.

Room 910, Ke Lun Mansion
12A Guanghua Road
Chaoyang District
Beijing 100020
Phone +86 10 6581 8396
Fax +86 10 6581 8381

France

Special Metals Services SA

17 Rue des Frères Lumière
69680 Chassieu (Lyon)
Phone +33 (0) 4 72 47 46 46
Fax +33 (0) 4 72 47 46 59

Germany

Special Metals Deutschland Ltd.

Postfach 20 04 09
40102 Düsseldorf
Phone +49 (0) 211 38 63 40
Fax +49 (0) 211 37 98 64

Hong Kong

Special Metals Pacific Pte. Ltd.

Unit A, 17th Floor, On Hing Bldg
1 On Hing Terrace
Central, Hong Kong
Phone +852 2439 9336
Fax +852 2530 4511

India

Special Metals Services Ltd.

No. 60, First Main Road, First
Block
Vasanth Vallabha Nagar
Subramanyapura Post
Bangalore 560 061
Phone +91 (0) 80 2666 9159
Fax +91 (0) 80 2666 8918

Italy

Special Metals Services SpA

Via Assunta 59
20054 Nova Milanese (MI)
Phone +390 362 4941
Fax +390 362 494224

The Netherlands

Special Metals Service BV

Postbus 8681
3009 AR Rotterdam
Phone +31 (0) 10 451 44 55
Fax +31 (0) 10 450 05 39

Singapore

Special Metals Pacific Pte. Ltd.

24 Raffles Place
#27-04 Clifford Centre
Singapore 048621
Phone +65 6532 3823
Fax +65 6532 3621

Affiliated Companies

Special Metals Welding Products

1401 Burriss Road
Newton, NC 28658, U.S.A.
Phone +1 (828) 465-0352
+1 (800) 624-3411
Fax +1 (828) 464-8993

Canada House

Bidavon Industrial Estate
Waterloo Road
Bidford-On-Avon
Warwickshire B50 4JN, U.K.
Phone +44 (0) 1789 491780
Fax +44 (0) 1789 491781

Controlled Products Group

590 Seaman Street, Stoney Creek
Ontario L8E 4H1, Canada
Phone +1 (905) 643-6555
Fax +1 (905) 643-6614

A-1 Wire Tech, Inc.

A Special Metals Company

4550 Kishwaukee Street
Rockford, IL 61109, U.S.A.
Phone +1 (815) 226-0477
+1 (800) 426-6380
Fax +1 (815) 226-0537

Rescal SA

A Special Metals Company

200 Rue de la Couronne des Prés
78681 Epône Cédex, France
Phone +33 (0) 1 30 90 04 00
Fax +33 (0) 1 30 90 02 11

DAIDO-SPECIAL METALS Ltd.

A Joint Venture Company

Daido Shinagawa Building
6-35, Kohnan 1-chome
Minato-ku, Tokyo 108-0057, Japan
Phone +81 (0) 3 5495 7237
Fax +81 (0) 3 5495 1853

The data contained in this publication is for informational purposes only and may be revised at any time without prior notice. The data is believed to be accurate and reliable, but Special Metals makes no representation or warranty of any kind (express or implied) and assumes no liability with respect to the accuracy or completeness of the information contained herein. Although the data is believed to be representative of the product, the actual characteristics or performance of the product may vary from what is shown in this publication. Nothing contained in this publication should be construed as guaranteeing the product for a particular use or application.

